

Simple Respiratory Protection—Evaluation of the Filtration Performance of Cloth Masks and Common Fabric Materials Against 20–1000 nm Size Particles

SAMY RENGASAMY^{1*}, BENJAMIN EIMER² and RONALD E. SHAFFER¹

¹National Institute for Occupational Safety and Health/National Personal Protective Technology Laboratory—Technology Research Branch, 626 Cochran Mill Road, Pittsburgh, PA 15236, USA;

²Technology Research Branch, URS Corp., Pittsburgh, PA, USA

Received 4 February 2010; in final form 10 May 2010; published online 28 June 2010

A shortage of disposable filtering facepiece respirators can be expected during a pandemic respiratory infection such as influenza A. Some individuals may want to use common fabric materials for respiratory protection because of shortage or affordability reasons. To address the filtration performance of common fabric materials against nano-size particles including viruses, five major categories of fabric materials including sweatshirts, T-shirts, towels, scarves, and cloth masks were tested for polydisperse and monodisperse aerosols (20–1000 nm) at two different face velocities (5.5 and 16.5 cm s⁻¹) and compared with the penetration levels for N95 respirator filter media. The results showed that cloth masks and other fabric materials tested in the study had 40–90% instantaneous penetration levels against polydisperse NaCl aerosols employed in the National Institute for Occupational Safety and Health particulate respirator test protocol at 5.5 cm s⁻¹. Similarly, varying levels of penetrations (9–98%) were obtained for different size monodisperse NaCl aerosol particles in the 20–1000 nm range. The penetration levels of these fabric materials against both polydisperse and monodisperse aerosols were much higher than the penetrations for the control N95 respirator filter media. At 16.5 cm s⁻¹ face velocity, monodisperse aerosol penetrations slightly increased, while polydisperse aerosol penetrations showed no significant effect except one fabric mask with an increase. Results obtained in the study show that common fabric materials may provide marginal protection against nanoparticles including those in the size ranges of virus-containing particles in exhaled breath.

Keywords: fabric material; H1N1; H5N1; infectious aerosol; influenza; pandemic; particle penetration; respiratory protection

INTRODUCTION

The outbreaks of avian influenza A (H5N1) and the recent novel influenza virus A (H1N1) pandemic are major health problems (WHO, 2006, 2009). To reduce exposure to infectious influenza aerosols, several government agencies and nongovernment organizations have recommended a number of non-pharmaceutical interventions, including respiratory

protection. The Centers for Disease Control and Prevention (CDC) recommends the use of National Institute for Occupational Safety and Health (NIOSH)-approved respirators for reducing exposure to infectious aerosols such as those that cause severe acute respiratory syndrome (SARS) and novel influenza (H1N1) (CDC, 2001, 2003, 2004, 2009). The use of large number of respirators created a demand during the spread of SARS in the USA (Srinivasan *et al.*, 2004). Recently, CDC predicted that the need for disposable N95 respirators could exceed 90 million for the protection of healthcare

*Author to whom correspondence should be addressed.
Tel: +412-386-6853; fax: +412-386-5250;
e-mail: AREngasamy@cdc.gov

workers for an outbreak of 42 days of influenza A (H5N1), indicating a possible shortage of respirators (Bailar *et al.*, 2006; CDC, 2006).

The issue of a respirator shortage during a widespread influenza pandemic was addressed by the Institute of Medicine (IOM), which released a report entitled 'Reusability of Facemasks during an Influenza Pandemic. Facing the flu' (Bailar *et al.*, 2006). One of the recommendations was to conduct research on the effectiveness of woven cloth masks for the transmission of influenza virus because cloth masks may be the only option available for some individuals during a pandemic. Research on alternative respiratory protective materials, including common fabric materials such as T-shirts, handkerchiefs, and scarves, was also recommended (Bailar *et al.*, 2006). In the absence of respirators, some individuals may use improvised common fabric materials for respiratory protection while entering a contaminated environment, such as when caring for an infected family member at home. These household materials are not designed for respiratory protection and their use may provide a false sense of protection because their effectiveness against larger and <1000 nm size particles including viruses is not well understood. This indicates that further studies are needed to better understand the filtration performance of cloth masks and common fabric materials against a wide range of particle sizes, including the size of many viruses.

The knowledge on the filtration performance of improvised materials for particulates is limited, however. Previous studies challenged the improvised materials with large-size biological and inert particles and reported varying levels of protection for different size particles (Guyton *et al.*, 1959; Cooper *et al.*, 1983a,b). In one study, the filtration efficiency of a number of fabric materials was tested using human subjects. The authors reported that the filtration efficiency of single layer of bath towel, cotton shirt, handkerchief, and other materials was in the 28–73% range against *Bacillus globigii* aerosols of 2000 nm mass median diameter (Guyton *et al.*, 1959). Another study measured the effectiveness factor obtained from filtration efficiency and pressure drop for different common fabric materials using a manikin (Cooper *et al.*, 1983a). Fabric materials were challenged with mineral oil aerosol particles of 410–4800 nm diameter size and the effectiveness factor calculated. For many fabric materials including shirt, sheet, towel, and handkerchief, the effectiveness factor decreased with decreasing particle size from 4800 to 410 nm, indicating further decrease in the respiratory protection

for virus-containing particles <410 nm (Cooper *et al.*, 1983a).

Recent studies showed that patients, as well as control subjects, generate significant levels of sub-micron as well as larger size particles including the size of many viruses during breathing, coughing, and talking (Fairchild and Stampfer, 1987; Papineni and Rosenthal, 1997; Edwards *et al.*, 2004; Yang *et al.*, 2007; Fabian *et al.*, 2008; Blachere *et al.*, 2009; Lindsley *et al.*, 2010). Although some viruses can be quite small (~20 nm), they are often generated by humans as larger size particles (e.g. attached to mucus secretions). For example, one study (Fabian *et al.*, 2008) showed 87% of particles in exhaled breath of influenza-infected patients were under 1000 nm in diameter and the rest of the particles larger than that size. Similarly, the transmission of infectious diseases through exposure to smaller and >1000 nm size aerosols has been reviewed (Fiegel *et al.*, 2006; Hall, 2007). Although much debate still exists on the relative contributions of the various routes of disease transmission (e.g. inhalation, contact, and droplet) (IOM, 2009), infected individuals produce smaller size particles (<1000 nm) that can travel long distances and larger size particles (~10000 nm) capable of reaching shorter distances. Some individuals may improvise fabric materials for emergency respiratory protection to reduce inhalation of infectious aerosols, indicating the need for further studies to assess their filtration performance against a wide range of particle sizes. In this study, household fabric materials and cloth masks were challenged with polydisperse as well as monodisperse particles in the 20–1000 nm size range, which include the size of many viruses and initial penetration levels measured and compared with those values obtained for N95 respirator filter media. In this study, we hypothesized that cloth masks and fabric materials would capture some aerosol but would exhibit high variability because they were not designed for that purpose.

MATERIALS AND METHODS

Fabric materials

Common fabric materials of five major categories including sweatshirts, T-shirts, towels, scarves, and cloth masks were selected for aerosol penetration tests (Table 1). Table 1 also shows the fiber composition of fabric materials and the resistance levels measured at 5.5 cm s⁻¹ face velocity. The fiber composition for cloth masks is not available. Fabric materials for each category were randomly selected

Table 1. Fabric materials tested for particle penetration measurements

| Fabric material | Description | Model 1 | Model 2 | Model 3 |
|-----------------|-----------------------|------------------------------------|------------------------------|-------------------------------|
| Cloth mask | Brand name | Respro Bandit Mask | Breathe Health Cloth Mask | Breathe Health Fleece Mask |
| | Fiber composition | Not available | Not available | Not available |
| | Resistance (mm water) | 2.0 ± 0.3 | 3.2 ± 0.7 | 1.2 ± 0.1 |
| Sweatshirt | Brand name | Norma Kamali Tunic | Hanes | Faded Glory |
| | Fiber composition | 85% Cotton/ 15% polyester | 70% Cotton/ 30% polyester | 60% Cotton/ 40% polyester |
| | Resistance (mm water) | 2.0 ± 0.1 | 1.1 ± 0.1 | 0.4 ± 0.1 |
| T-shirt | Brand name | Dickies | Hanes | Faded Glory |
| | Fiber composition | 99% Cotton/ 1% polyester | 100% Cotton | 60% Cotton/ 40% polyester |
| | Resistance (mm water) | 1.6 ± 0.2 | 1.6 ± 0.1 | 0.9 ± 0.1 |
| Towel | Brand name | Pem America | Pinzon | Aquis |
| | Fiber composition | 100% Cotton | 100% Cotton | 80% Polyester/ 20% nylon |
| | Resistance (mm water) | 3.8 ± 0.2 | 7.9 ± 0.8 | 3.7 ± 0.2 |
| Scarf | Brand name | Today's Gentleman Pocket square | Walmart Fleece | Seed Supply Cotton |
| | Fiber composition | 100% Cotton | 100% Polyester | 100% Cotton |
| | Resistance (mm water) | 5.9 ± 0.1 | 2.0 ± 0.1 | 1.4 ± 0.1 |

Fabric material composition and airflow resistance measured at 5.5 cm s⁻¹ face velocity. 1 mm water gauge = 0.133 kPa.

from three different manufacturers based on availability. The commercial cloth masks were advertised as pollution and allergen masks and did not make any claim as to their effectiveness for submicron-size particles. It should be noted that none of the other fabric materials was designed to be used as a filtering media. N95 respirator filter media was tested in parallel with the fabric materials for comparison of the filtration performance against submicron-size aerosol particles.

Polydisperse aerosol penetration test method

Three samples from each fabric materials were tested for polydisperse NaCl aerosol (75 ± 20 nm count median diameter and a geometric standard deviation not exceeding 1.86) penetrations with a TSI 8130 Automated Filter Tester (TSI 8130) used for NIOSH particulate respirator certification (NIOSH, 2007). Penetration levels for 100 cm² samples were measured at two different face velocities 5.5 and 16.5 cm s⁻¹ corresponding to 33 and 99 l min⁻¹ flow rates. A standard face velocity of 5.3 cm s⁻¹ is employed for testing various filter media. In this study, a face velocity closer to this value, i.e. 5.5 cm s⁻¹,

and a relatively higher face velocity, 16.5 cm s⁻¹, were employed for testing the filtration performance of fabric materials. The flow rates are based on the area of the fabric material tested to achieve the face velocities employed in the study. Initial penetration levels of NaCl particles were measured for 1 min with no loading as conducted in the NIOSH 42 CFR 84 test protocol. Percentage penetration was determined as the ratio of particle concentration downstream to upstream multiplied by 100. Polydisperse aerosol is commonly used for filtration performance testing and allows comparison to standard filters made (N95, P2, P3, high efficiency particulate air, etc.).

Monodisperse aerosol penetration test method

Another set of three samples from each group of the same fabric models was tested against monodisperse NaCl particles using a TSI 3160 Fractional Efficiency Tester (TSI 3160) as described previously (Rengasamy *et al.*, 2007). Similar to polydisperse aerosols, penetration levels for 100 cm² samples were measured at face velocities 5.5 and 16.5 cm s⁻¹. Initial percentage penetration levels

for 10 different monodisperse aerosols (20, 30, 40, 50, 60, 80, 100, 200, 300, and 400 nm) were measured for each sample. These monodisperse aerosol tests were conducted to better understand the filtration performance against <400 nm size particles. This size range is necessary to determine the aerosol size range of minimum efficiency.

Penetration of NaCl particles as a function of particle size from 500 to 1000 nm

Penetration levels for larger size particles (500–1000 nm) were measured as a function of particle size. Polydisperse NaCl aerosols were generated using a constant output atomizer (Model 3076; TSI, Inc.) and passed through a dryer, a ^{85}Kr neutralizer, and then into the Plexiglas box containing the test fabric material. The upstream and downstream aerosol number concentrations and size distributions (500–1000 nm range) were measured for 2 min alternately using a scanning mobility particle sizer (SMPS 3080; TSI, Inc.) in scanning mode and an ultrafine condensation particle counter as described previously (Rengasamy *et al.*, 2009a). Percentage penetration was calculated from the ratio of the particle number concentration downstream to the concentration upstream. These monodisperse aerosol tests were conducted to better understand the filtration performance against 500–1000 nm size particles.

Data analysis

The data were analyzed using the SigmaPlot® (Jandel Corporation) computer program. Average penetration values and 95% confidence intervals were calculated for each model.

RESULTS

Polydisperse aerosol penetrations

Average penetration levels for the three different cloth masks were between 74 and 90%, while N95 filter media controls showed 0.12% at 5.5 cm s^{-1} face velocity (Fig. 1). The penetration levels increased significantly for the N95 control filter media but remained <5%, while none of the fabric materials showed any significant increase at 16.5 cm s^{-1} face velocity. Figure 2 shows polydisperse aerosol penetration levels for sweatshirts and T-shirts. Of the three sweatshirts, one model (Hanes) showed 40% penetration level at 5.5 cm s^{-1} , which increased to 57% at 16.5 cm s^{-1} face velocity. The other two models (Norma Kamali and Faded Glory) showed penetration levels in the 70–82% range at both

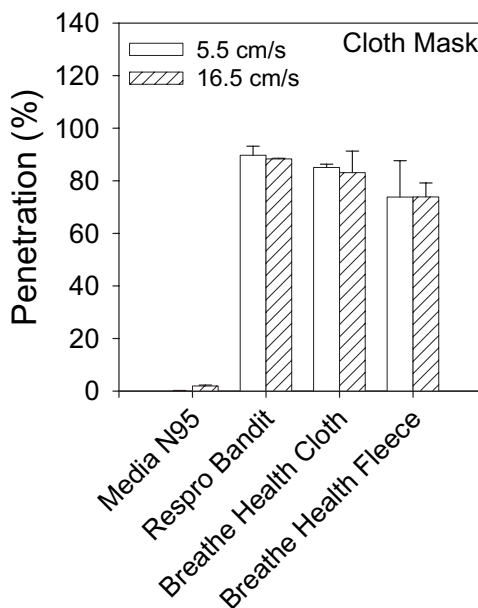


Fig. 1. Polydisperse NaCl aerosol penetration levels for cloth masks at two different face velocities. Error bars indicate 95% confidence level.

5.5 and 16.5 cm s^{-1} face velocities (Fig. 2a). At the same time, T-shirts showed penetration levels >86% at 5.5 cm s^{-1} with no significant increase at 16.5 cm s^{-1} (Fig. 2b). Average penetration levels for the three different model towels and scarves were in the 60–66% and 73–89% ranges, respectively, with no significant increase at 16.5 cm s^{-1} (Fig. 3a,b). Table 1 shows airflow resistance (in millimeter water) at 5.5 cm s^{-1} face velocity. In general, the resistance levels were less than or comparable to N95 filter material employed in the study (9.8 ± 0.2 cm water gauge; 1 cm water gauge = 1.33 kPa). A cotton towel model (Pinzon) and a scarf material (Today's Gentleman) showed slightly higher resistance levels than the other fabric materials. Slightly higher airflow resistance levels were obtained at 16.5 cm s^{-1} .

Monodisperse aerosol penetrations

Penetration levels for monodisperse aerosol particle (20–400 nm range) were combined with those for 500–1000 nm range particles measured as a function of particle size. For the cloth masks, monodisperse aerosol penetration levels (35–68%) for 20 nm size particles increased steadily, reached maximum (73–82%) at 100 nm range, plateaued up to 400 nm, and increased slightly up to 1000 nm at 5.5 cm s^{-1} face velocity (Fig. 4a). Slightly higher penetration levels were obtained at 16.5 cm s^{-1} face

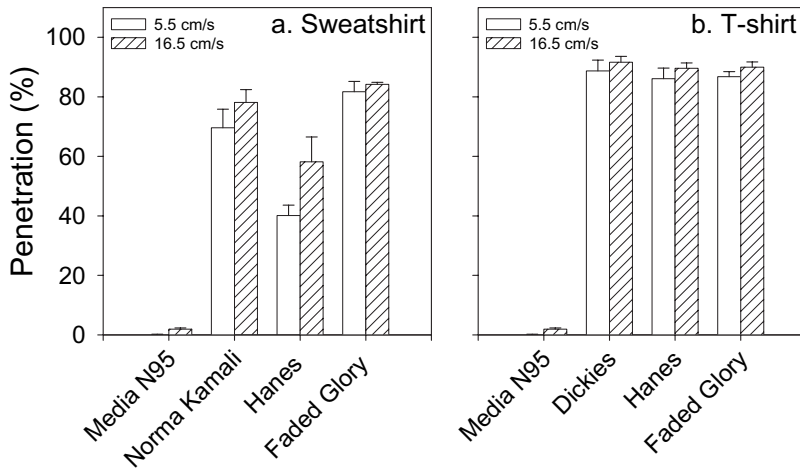


Fig. 2. Polydisperse NaCl aerosol penetration levels for sweatshirts and T-shirts at two different face velocities. Error bars indicate 95% confidence level.

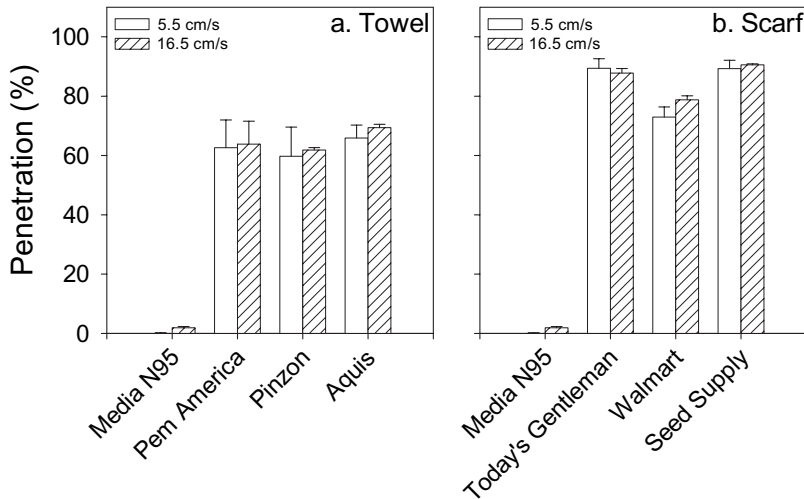


Fig. 3. Polydisperse NaCl aerosol penetration levels for towels and scarves at two different face velocities. Error bars indicate 95% confidence level.

velocity for the different size particles (20–1000 nm range) (Fig. 4b). Penetration levels for the three sweatshirt and T-shirt models were, respectively, in the 30–61% and 56–79% ranges for 20-nm size particles and increased to 80–93% and 89–97% for 1000 nm particles (Fig. 5a,c). A slight increase in penetration levels was obtained for 20–1000 nm size particles, which remained the same or decreased slightly with increasing particle sizes at 16.5 cm s⁻¹ face velocity (Fig. 5b,d). In the case of towels and scarves, penetration levels varied from 9 to 74% for 20 nm size particles and increased monotonically at 5.5 cm s⁻¹ face velocity (Fig. 6a,c).

Penetration levels of different size particles increased at 16.5 cm s⁻¹ face velocity at varying levels (Fig. 6b,d).

DISCUSSION

The results obtained in the study showed that cloth masks and other fabric materials tested in the study had 40–90% instantaneous penetration levels when challenged with polydisperse NaCl aerosols employed in the NIOSH particulate respirator test protocol at a face velocity of 5.5 cm s⁻¹. Similarly, varying levels of penetrations (9–98%) were

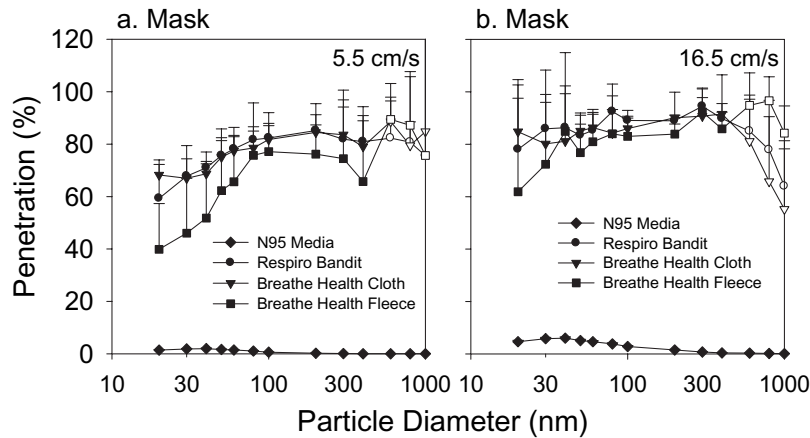


Fig. 4. Monodisperse aerosol penetration levels for cloth masks at two different face velocities. Error bars indicate 95% confidence level (closed symbols, TSI 3160 and open symbols, SMPS).

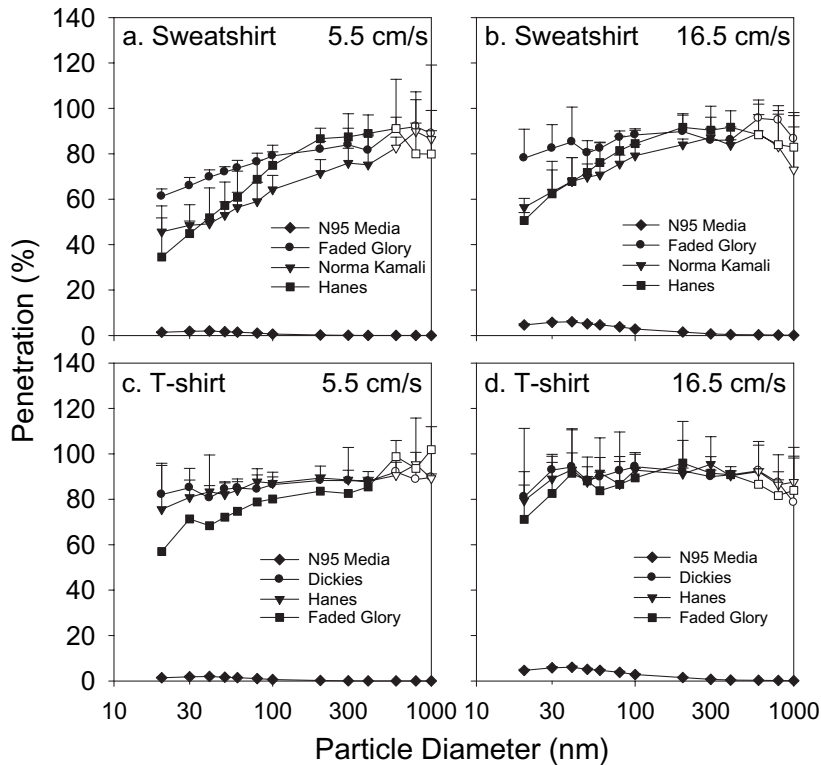


Fig. 5. Monodisperse aerosol penetration levels at two different face velocities for sweatshirts (a and b) and T-shirts (c and d). Error bars indicate 95% confidence level. (closed symbols, TSI 3160 and open symbols, SMPS).

obtained for different size monodisperse NaCl aerosol particles in the 20–1000 nm range. Monodisperse aerosol penetration curves for many fabric materials were similar to the curve for a mechanical filter indicating that electret charge was not incorporated in

the fabric materials tested in the study. The penetration levels for these fabric materials against polydisperse, as well as monodisperse aerosols, were much higher than the values for the control N95 respirator filter media. A poor filtration performance is

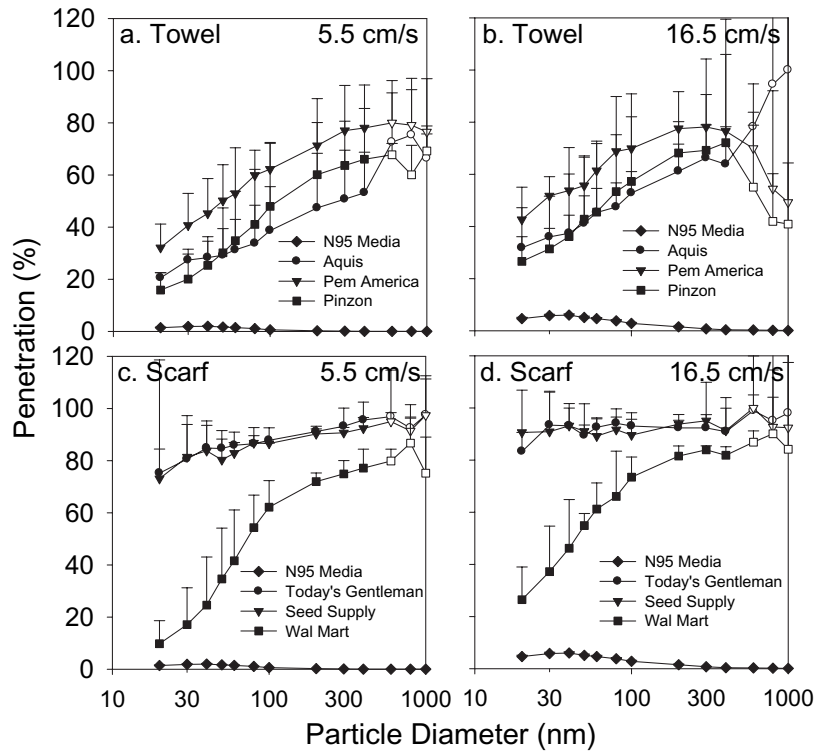


Fig. 6. Monodisperse aerosol penetration levels at two different face velocities for towels (a and b) and scarves (c and d). Error bars indicate 95% confidence level. (closed symbols, TSI 3160 and open symbols, SMPS).

expected for improvised fabric materials because these materials are not designed for respiratory protection.

The wide variation in penetration levels obtained for many fabric materials tested in our study agree with the penetration results reported previously (Guyton *et al.*, 1959; Cooper *et al.*, 1983a). For example, the filtration efficiency (i.e. inverse of the penetration) of fabric materials was in the range of 3–33% (penetration range 67–97%) for 1000 nm particles at 5.5 cm s⁻¹ face velocity that is comparable to the filtration efficiency (27–73%) of single-layer fabric materials against *B. globigii* particles (2000 nm) at a breathing flow rate of 10 l min⁻¹ (Guyton *et al.*, 1959). The increase in efficiency can be attributed to the efficient capturing of larger size *B. globigii* particles. Similarly, the penetration values measured in our study 56–94% and 67–97% for 400 and 1000 nm size particles, respectively, at 5.5 cm s⁻¹ face velocity are similar compared to 54 and 59% penetrations for 400 and 1000 nm size particles, respectively, at 1.5 cm s⁻¹ face velocity reported previously (Cooper *et al.*, 1983a).

The filtration efficiency of improvised fabric materials is comparable to some commonly used

Federal Drug Agency-cleared surgical masks and unapproved dust masks (Oberg and Brosseau, 2008; Rengasamy *et al.*, 2008; Rengasamy *et al.*, 2009b). For example, previous studies showed that some surgical masks had high penetration levels against similar size polydisperse as well as monodisperse aerosols at a similar face velocity (Rengasamy *et al.*, 2009b). Two of the five surgical masks showed 51–89% penetration levels against polydisperse aerosols. Similarly, three dust mask models had high penetration levels (81–89%) for polydisperse aerosol particles (Rengasamy *et al.*, 2008). Thus, the penetration results obtained in the study indicate that the filtration performance of fabric materials is similar in some aspects to some surgical masks to reduce the transmission of infectious diseases. However, this study did not evaluate the fabric materials for protection against droplets and liquid splashes.

The use of fabric materials may provide only minimal levels of respiratory protection to a wearer against virus-size submicron aerosol particles (e.g. droplet nuclei). This is partly because fabric materials show only marginal filtration performance against virus-size particles when sealed around the edges. Face seal leakage will further decrease the

respiratory protection offered by fabric materials. As expected, a previous study using a manikin showed greater particle penetration for loosely held fabric materials than fully sealed materials around edges (Guyton *et al.*, 1959). Interestingly, however, some studies have reported that improvised fabric materials can provide a good fit and measurable protection level against test aerosols (Dato *et al.*, 2006; Sandee *et al.*, 2009). In one study, fit factors between 13 and 67 were obtained for three subjects using hand-fashioned masks out of a Hanes T-shirt, a modest level of protection to the wearer (Dato *et al.*, 2006). Similarly, home-made face masks made of tea cloths tested on human subjects provided marginal protection as measured by a PortaCount® Plus (TSI, Inc.) that also uses 20–1000 nm size ambient air particles compared to surgical and CE-marked FFP2 masks (Sandee *et al.*, 2009). The authors reported protection factor levels of 2–3, 4–6, and 66–141 for tea cloths, surgical masks, and FFP2 masks, respectively, under various test conditions. The fabric materials tested in our study might also be expected to provide marginal levels of respiratory protection for 20–1000 nm aerosols (droplet nuclei). Fabric materials may provide respiratory protection levels (i.e. total inward leakage) similar to the levels obtained using some surgical masks, which have been measured to be <10 (Oberg and Brosseau, 2008). Thus, the use of improvised fabric materials may be of some value compared to no protection at all when respirators are not available. Moreover, fabric materials would not suffer from limited supplies unlike respirators and surgical masks for emergency protection.

Some of the fabric materials tested in this study had relatively better filtration performance than others. For example, the Hanes sweatshirt showed less penetration levels against polydisperse aerosols at 5.5 cm s⁻¹ face velocity compared to other fabric materials. Similarly, monodisperse aerosol penetration values for particles <60 nm size were less for Hanes sweatshirt. However, the penetration values for >60 nm size particles were higher similar to the penetrations for other sweatshirts and the reason for the discrepancy is not clear. The filtration performance of the towels (Aquis, Pinzon, and Pem America) and one scarf (Walmart) against <100 nm size monodisperse aerosol particles was relatively better than the other fabric materials. Moreover, filtration performance of the fabric materials showed no correlation with the airflow resistance levels. Filtration of polydisperse aerosol particles was effective by 100% cotton fabrics in one case, while 100% polyester, 100% cotton, or cotton/polyester combination was

better for nanoparticle (<100 nm) range. Filtration performance of the fabric material cannot be estimated *a priori* from material composition because it is mostly dependent on fiber characteristics, including diameter, charge, and packing density. Moreover, the finished fabric products do not carry information on fiber properties involved in particle filtration. Thus, the selection process for a better performing improvised fabric material may be difficult for a common user. In spite of the poor performance, fabric materials may provide some level of protection against the transmission of infectious aerosols when used in combination with other protective measures. Recently, a review paper analyzed the data obtained from seven case-control studies on the intervention measures of SARS transmission (Jefferson *et al.*, 2009). The authors concluded that a combination of several measures including the use of respiratory protection devices, gloves, and other hygienic practices may reduce the spread of infectious diseases considerably than by a single method. Moreover, cloth masks and fabric materials covering the mouth and nose may serve as a reminder to not touch those areas with the hands serving to minimize contact transmission and reduce exposure to liquid splashes and droplets, although these premises would need to be confirmed experimentally.

The limitations of our study include that only a few types of fabric materials were tested in the study. Some fabric materials not tested in the study may perform better. None of the materials had been worn or laundered, which could also affect filtration performance. Moreover, face seal leakage of aerosol particles was not measured, which is a critical component of respiratory protection. Further studies on respiratory protection of common fabric materials on human subjects for an even wider size range (20–5000 nm) of aerosol particles (e.g. to include more data on filtration performance against droplets) would be helpful to better assess the value of common fabric materials to reduce exposure to infectious aerosols.

CONCLUSION

Common fabric materials and cloth masks showed a wide variation in penetration values for polydisperse (40–90%) as well as monodisperse aerosol particles in the 20–1000 nm range (40–97%) at 5.5 cm s⁻¹ face velocity. The penetration levels obtained for fabric materials against both polydisperse and monodisperse aerosols were much higher than the value for the control N95 respirator filter media but were in the range found for some surgical masks

in previous studies. Penetrations of monodisperse aerosol particles slightly increased at 16.5 cm s⁻¹ face velocity, while polydisperse aerosols showed no significant effect except one fabric mask with an increase. The penetration values obtained for common fabric materials indicate that only marginal respiratory protection can be expected for submicron particles taking into consideration face seal leakage.

FUNDING

National Institute for Occupational Safety and Health (CAN #927 Z1NT).

Acknowledgements—The authors acknowledge National Institute for Occupational and Safety and Health (NIOSH) colleagues including Debra Novak, Rick Ehrenberg, and Ta-Chih Hsiao for their critical review of the manuscript and suggestions. We thank Hollingsworth & Vose Company for providing N95 respirator filter media.

Disclaimer—Mention of commercial product or trade name does not constitute endorsement by the NIOSH. The findings and conclusions of this report are those of the authors and do not necessarily represent the views of the NIOSH.

REFERENCES

- Bailor JC, Brosseau LM, Cohen HJ *et al.* (2006) Reusability of facemasks during an influenza pandemic. Facing the flu. Washington, DC: Institute of Medicine, National Academies Press.
- Blachere FM, Lindsley WG, Pearce TA *et al.* (2009) Measurement of airborne influenza virus in a hospital emergency department. *Clin Infect Dis*; 48: 438–40.
- CDC. (2001) Interim recommendations for the selection and use of protective clothing and respirators against biological agents. Atlanta, GA: Centers for Disease Control and Prevention.
- CDC. (2003) Interim domestic guidance on the use of respirators to prevent the transmission of SARS. Atlanta, GA: Centers for Disease Control and Prevention, Department of Health and Human Services, Public Health Service, Tuberculosis Control Division.
- CDC. (2004) Interim recommendations for the selection and use of protective clothing and respirators against biological agents. Atlanta, GA: Centers for Disease Control and Prevention, Public Health Service, Tuberculosis Control Division.
- CDC. (2006) Estimated number of masks needed, by type and setting, for a severe influenza pandemic. Atlanta, GA: Centers for Disease Control and Prevention.
- CDC. (2009) Interim recommendations for facemask and respirator use to reduce novel influenza A (H1N1) virus transmission. Atlanta, GA: Centers for Disease Control and Prevention.
- Cooper DW, Hinds WC, Price JM. (1983a) Emergency respiratory protection with common materials. *Am Ind Hyg Assoc J*; 44: 1–6.
- Cooper DW, Hinds WC, Price JM *et al.* (1983b) Common materials for emergency respiratory protection: leakage tests with a manikin. *Am Ind Hyg Assoc J*; 44: 720–6.
- Dato VM, Hostler D, Hahn ME. (2006) Simple respiratory mask. *Emerg Infect Dis*; 12: 1033–34.
- Edwards DA, Man JC, Brand P *et al.* (2004) Inhaling to mitigate exhaled bioaerosols. *Proc Natl Acad Sci U S A*; 101: 17383–8.
- Fabian P, Mcdevitt JJ, Dehaan WH *et al.* (2008) Influenza virus in human exhaled breath: an observational study. *PloS One*; 3: 1–6.
- Fairchild CI, Stampfer JF. (1987) Particle concentration in exhaled breath. *Am Ind Hyg Assoc J*; 48: 948–58.
- Fiegel J, Clarke R, Edwards DA. (2006) Airborne infectious disease and the suppression of pulmonary bioaerosols. *Drug Discov Today*; 11: 51–7.
- Guyton HG, Decker HM, Anton GT. (1959) Emergency respiratory protection against radiological and biological aerosols. *AMA Arch Ind Health*; 20: 9–13.
- Hall CB. (2007) The spread of influenza and other respiratory viruses: complexities and conjectures. *Clin Infect Dis*; 45: 353–9.
- IOM. (2009) Respiratory protection for healthcare workers in the workplace against novel H1N1 influenza A: a letter report. Washington, DC: The National Academic Press.
- Jefferson T, Del Mar C, Dooley L *et al.* (2009) Physical interventions to interrupt or reduce the spread of respiratory viruses: systematic review. *Br Med J*; 339: b3675. doi: 10.1136/bmj.b3675.
- Lindsley WG, Blachere FM, Davis KA *et al.* (2010) Distribution of airborne influenza virus and respiratory syncytial virus in an urgent care medical clinic. *Clin Infect Dis*; 50: 693–8.
- NIOSH. (2007) Procedure no. TEB-APR-STP-0059, revision 2.0. Determination of particulate filter efficiency level for N95 series filters against solid particulates for non-powered, air purifying respirators standard testing procedure (STP). Pittsburgh, PA: DHHS, Centers for Disease Control and Prevention, National Institute for Occupational Safety and Health, National Personal Protective Technology Laboratory. Available at <http://www.cdc.gov/niosh/npptl/stps/pdfs/TEB-APR-STP-0059.pdf>. Accessed 9 December 2009.
- Oberg T, Brosseau LM. (2008) Surgical mask filter and fit performance. *Am J Infect Control*; 36: 276–82.
- Papineni RS, Rosenthal FS. (1997) The size distribution of droplets in the exhaled breath of health human subjects. *J Aerosol Med*; 10: 105–16.
- Rengasamy S, Eimer B, Shaffer RE. (2008) Nanoparticle filtration performance of commercially available dust masks. *J Int Soc Respir Prot*; 25: 27–41.
- Rengasamy S, Eimer B, Shaffer RE. (2009a) Comparison of nanoparticle filtration performance of NIOSH-approved and CE marked filtering-facepiece respirators. *Ann Occup Hyg*; 53: 117–28.
- Rengasamy S, Miller AK, Eimer B *et al.* (2009b) Filtration performance of FDA-cleared surgical masks. *J Int Soc Respir Prot*; 26: 54–70.
- Rengasamy A, Verbofsky R, King WP *et al.* (2007) Nanoparticle penetration through NIOSH-approved N95 filtering-facepiece respirators. *J Int Soc Respir Prot*; 24: 4959.
- Sandee MV, Teunis P, Sabel R. (2009) Professional and home-made face masks reduce exposure to respiratory infections among the general population. *PloS One*; 3: e2618.
- Srinivasan A, Jernign DB, Liedtke L *et al.* (2004) Hospital preparedness for severe acute respiratory syndrome in the United States: views from a national survey of infectious diseases consultants. *Clin Infect Dis*; 39: 272–4.

- WHO. (2006) Avian influenza ("bird flu"). Copenhagen, Denmark: World Health Organization. Available at http://www.who.int/mediacentre/factsheets/avian_influenza/en/print.html. Accessed 20 August 2009.
- WHO. (2009) Influenza A (H1N1): pandemic alert phase 6 declared, of moderate severity. WHO/Europe—outbreak update. Copenhagen, Denmark: World Health Organization. Available at http://www.euro.who.int/influenza/AH1N1/20090611_11. Accessed 29 July 2009.
- Yang S, Lee GWM, Chen C-M *et al.* (2007) The size and concentration of droplets generated by coughing in human subjects. *J Aerosol Med*; 20: 484–94.

Copyright of Annals of Occupational Hygiene is the property of Oxford University Press / UK and its content may not be copied or emailed to multiple sites or posted to a listserv without the copyright holder's express written permission. However, users may print, download, or email articles for individual use.